

Comment on “Ferroelectrically Induced Weak Ferromagnetism by Design”

The question of how ferroelectric polarization is coupled to magnetism in magnetoelectric multiferroics is of considerable current interest. A recent Letter [1] analyzes the important “ ABO_3 ” class of perovskite multiferroics. A symmetry argument is presented that materials with antiferromagnetism on the B site lack linear magnetoelectric coupling $E_{PLM} = \mathbf{P} \cdot (\mathbf{L} \times \mathbf{M})$ in the free energy, unlike A-site antiferromagnets [1, 2]. Here $\mathbf{P}$ is polarization and $\mathbf{L}$ and $\mathbf{M}$ are antiferromagnetic and ferromagnetic moments.

This Comment presents a distinct analysis of E_{PLM} in ABO_3 multiferroics. We show that the argument of Ref. 1 does forbid E_{PLM} if the final low-symmetry phase contains only one distortion that, like $\mathbf{P}$, breaks all inversion symmetries. In reality there are multiple distortions in this symmetry class, and cross-terms generate E_{PLM} even in B-site materials, although the mechanism is different than in A-site materials. Additional differences can emerge between A-site and B-site materials under dynamical assumptions beyond the static free energy.

For concreteness we use BiFeO_3 , whose electronic structure has been extensively studied [3, 4]. Below 1100K it shows ferroelectric order with space group $R\bar{3}c$ and a 10-atom unit cell. In Ref. 1, the free energy is expanded from a model $R\bar{3}c$ phase with inversion center on Fe. For now, assume that the polarization $\mathbf{P}$ arises from relative motion of the ionic sublattices [3] along the threefold axis $\hat{\mathbf{z}}$. There is a 13.8° rotation α of the O octahedra around Fe atoms ($\alpha\hat{\mathbf{z}}$ is $\mathbf{D}$ in Ref. 1), which is even under Fe-site inversion I_B and odd under Bi-site inversion I_A . However, distortions beyond $\mathbf{P}$ and α must be present, either by counting $R\bar{3}c$ degrees of freedom or because the 1.4° counter-rotation of upper and lower triangles within an octahedron [5, 6] cannot be obtained by combining $\mathbf{P}$ and α .

Coordinates for an oxygen distortion β (Fig. 1) that causes this counter-rotation and is *orthogonal* to $\mathbf{P}$ are provided in EPAPS. The β distortion, like $\mathbf{P}$, is odd under I_A and I_B . For A-site magnetism, we have inversion eigenvalues $I_A\mathbf{L} = +\mathbf{L}$, and $I_B\mathbf{L} = -\mathbf{L}$. For B-site magnetism, $I_A\mathbf{L} = -\mathbf{L}$ and $I_B\mathbf{L} = +\mathbf{L}$. Allowed $\mathbf{L} \times \mathbf{M}$ terms are, with constants λ_1, λ_2 ,

$$\begin{aligned} F_A &= \lambda_1 \alpha \mathbf{P} \cdot (\mathbf{L} \times \mathbf{M}) + \lambda_2 \alpha \beta \hat{\mathbf{z}} \cdot (\mathbf{L} \times \mathbf{M}), \\ F_B &= \lambda_1 \alpha \beta \mathbf{P} \cdot (\mathbf{L} \times \mathbf{M}) + \lambda_2 \alpha \hat{\mathbf{z}} \cdot (\mathbf{L} \times \mathbf{M}). \end{aligned} \quad (1)$$

More generally, $\mathbf{P}$ is some $I_A = I_B = -1$ distortion, and E_{PLM} results from cross-terms

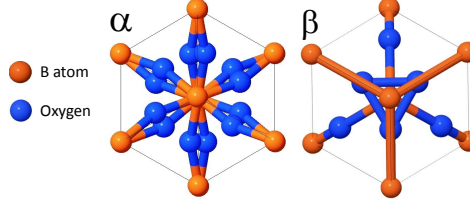


FIG. 1: Distortions α and β that reduce the ideal perovskite symmetry to $R3c$ (along threefold axis). The distortion β combines with α at order $\alpha\beta$ to give both the observed counter-rotation and a linear magnetoelectric coupling.

between $\mathbf{P}$ and other such distortions, here β . Magnetoelectric coupling should be sought in B-site structures with large β -type distortions as well as in A-site structures with large α .

Financial support from NSERC (R.d.S.) and WIN (J.E.M.) is acknowledged.

Rogério de Sousa¹ and Joel E. Moore²

¹Department of Physics and Astronomy, University of Victoria, Victoria, BC V8W 3P6, Canada; ²Department of Physics, University of California, and Materials Sciences Division, LBNL, Berkeley, CA 94720

-
- [1] C. Fennie, Phys. Rev. Lett. **100**, 167203 (2008).
 - [2] C. Ederer and C. Fennie, J. Phys.: Condens. Matter **20**, 434219 (2008).
 - [3] C. Ederer and N. A. Spaldin, Phys. Rev. B **71**, 060401(R) (2005).
 - [4] P. Ravindran, R. Vidya, A. Kjekshus, H. Fjellvag, and O. Eriksson, Phys. Rev. B **74**, 224412 (2006).
 - [5] F. Kubel and H. Schmid, Acta Cryst. **B46**, 698 (1990).
 - [6] The c and d $O - O$ bond lengths in [5] indicate this counter-rotation of 1.4° .

EXPLICIT CONSTRUCTION OF α AND β DISTORTIONS (APPENDIX TO COMMENT ON “FERROELECTRICALLY INDUCED WEAK FERROMAGNETISM BY DESIGN”)

It is convenient to use the following notation: Vectors written without parenthesis denote components along the primitive vectors: $x, y, z \equiv x\mathbf{a} + y\mathbf{b} + z\mathbf{c}$. A convenient set of primitive vectors for the 10-atom R3c unit cell is $\mathbf{a} = (0, 1, 1)$, $\mathbf{b} = (1, 0, 1)$, and $\mathbf{c} = (1, 1, 0)$. Here vectors with parenthesis are in a cartesian basis, and for convenience we choose the origin to be on top of a B atom. Note that if l, m, n is a set of integers, our notation implies that $x + l, y + m, z + n$ is equivalent to x, y, z apart from a Bravais vector translation.

For a general ABO_3 perovskite with R3c symmetry, both A and B atoms are located at Wyckoff 2a positions: The A atoms are located at x', x', x' and $x' + 1/2, x' + 1/2, x' + 1/2$, while the B atoms are located at x'', x'', x'' and $x'' + 1/2, x'' + 1/2, x'' + 1/2$.

The six oxygens must be located at Wyckoff 6b positions:

$$\begin{array}{ccc} x, y, z & z, x, y & y, z, x \\ y + \frac{1}{2}, x + \frac{1}{2}, z + \frac{1}{2} & x + \frac{1}{2}, z + \frac{1}{2}, y + \frac{1}{2} & z + \frac{1}{2}, y + \frac{1}{2}, x + \frac{1}{2} \end{array}$$

We may parametrize a set of *paraelectric* R3c structures (under the definition of polarization assumed for this example in the text, in which the polarization is well described as translation of the anion and cation lattices; if the definition of $\mathbf{P}$ changes, then that of β changes, but by counting such a β always exists) with two degrees of freedom α, β according to:

$$\begin{array}{ll} x' = \frac{1}{4} & x'' = 0 \\ x = -\frac{1}{4} + \alpha + \beta & y = \frac{3}{4} - \alpha + \beta \quad z = \frac{1}{4} - 2\beta \end{array}$$

This leads to the following atomic positions:

$$\begin{array}{l} \mathbf{R}_A = \frac{1}{4}, \frac{1}{4}, \frac{1}{4} \quad \frac{3}{4}, \frac{3}{4}, \frac{3}{4} \\ \mathbf{R}_B = 0, 0, 0 \quad \frac{1}{2}, \frac{1}{2}, \frac{1}{2} \\ \mathbf{R}_O = -\frac{1}{4} + \alpha + \beta, \frac{3}{4} - \alpha + \beta, \frac{1}{4} - 2\beta \quad \text{and cyclic permutations} \\ \quad \frac{5}{4} - \alpha + \beta, \frac{1}{4} + \alpha + \beta, \frac{3}{4} - 2\beta \quad \text{and cyclic permutations.} \end{array}$$

Note that any equivalent lattice site could equally well be chosen for the oxygen locations, e.g., the choice above $-\frac{1}{4}, \frac{3}{4}, \frac{1}{4}$ is equivalent to $-\frac{1}{4}, -\frac{1}{4}, \frac{1}{4}$, or $\frac{3}{4}, \frac{3}{4}, \frac{1}{4}$, and so on.

The α and β distortions defined in this way are non-polar, i.e., orthogonal to $\mathbf{P}$. To see this, consider the electric dipole moment produced by the oxygens,

$$P_O = Q_O \sum_{\mathbf{O}} \mathbf{R}_O = \sum_{l,m,n} [3 + 2(l + m + n)] \times 1, 1, 1. \quad (2)$$

This is seen to be independent of α, β and is equal to zero when summed over a symmetric set of lattice vectors (the electric dipole moment of the A and B atoms is also zero after a suitable summation). Direct computation shows that there is a counter-rotation by an angle proportional to $\alpha\beta$, as shown in Fig. 1 of the Comment.

The transformation properties under inversion on top of an A atom, I_A , and inversion on top of a B atom, I_B , are straightforward to compute from the atomic positions above. For I_B , just apply inversion directly to the $\mathbf{R}_O$ coordinates, while for I_A we must first subtract $1/4, 1/4, 1/4$, invert, and then add $1/4, 1/4, 1/4$. The final result is simple to state: When I_A is applied, the original structure is recovered if we apply the transformations $\alpha \rightarrow -\alpha$ and $\beta \rightarrow -\beta$. Under I_B , the original lattice will be recovered only if we apply $\alpha \rightarrow +\alpha$, and $\beta \rightarrow -\beta$. In summary,

$$\begin{aligned} I_A(\alpha, \beta) &= (-\alpha, -\beta) \\ I_B(\alpha, \beta) &= (\alpha, -\beta). \end{aligned} \quad (3)$$